

Starting point formulation – “All in one” professional grade, machine buffable vehicle polish – utilizing AQUACER 565, AQUACER 1031, BYK-L 9575, OPTIGEL-WX and DISPERBYK-2015


Sprayable car polish formulation with anti-hologram effect

Formulation

Position	Component	Supplier	Function	Weight (g)
1	Demineralized water		Solvent	69.40
2	Parmetol MBX (9 %)	Vink Chemicals	Biocide	0.20
3	OPTIGEL-WX (100 %)	BYK	Anti-settling and body	1.20
4	DISPERBYK-2015 (40 %)	BYK	Dispersing of abrasive	1.50
5	Sillitin Z 89 puriss (100 %)	Hoffmann Mineral	Abrasive	6.00
6	AQUACER 565 (30 %)	BYK	Surface protection	6.00
7	AQUACER 1031 (40 %)	BYK	Anti-hologram effect	1.20
8	Demineralized water		Solvent	12.50
9	BYK-L 9575 (60 %)	BYK	Gloss and slip	2.00
Total				100.00

Instructions

- Mix water, Parmetol MBX and OPTIGEL-WX at 800–1,000 rpm for 15 min.
- Add DISPERBYK-2015 and Sillitin Z 89 puriss under stirring.
- Stir the mixture at 2,000–3,000 rpm for 15 min.
- Mix AQUACER 565, AQUACER 1031 and demineralized water in a separate container.
- Stir the mixture for 15 min at 2,000–3,000 rpm.
- Combine the two solutions under stirring at 400–500 rpm and continue stirring for 5 min.
- Add BYK-L 9575 under stirring at 400–500 rpm over 3 min.
- Continue stirring at 400–500 rpm for 15 min.

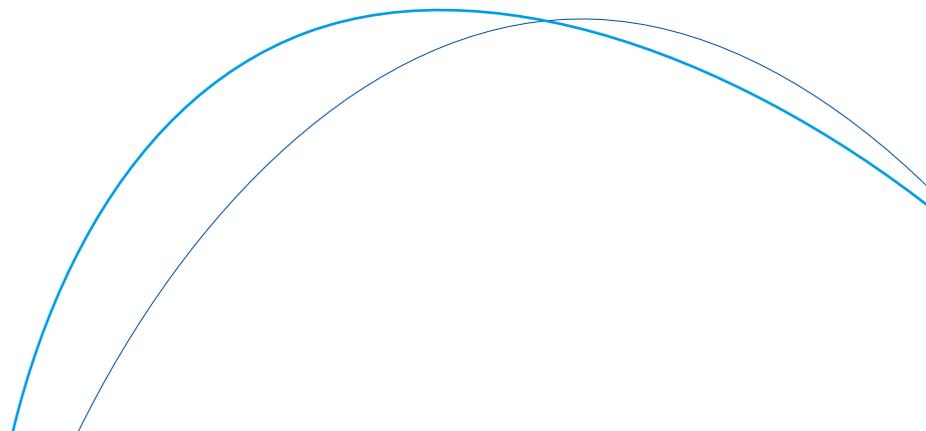

Characteristic data /specification

Data	Unit	Value
Solid wax content	%	2.30
Silicone content	%	1.20
Abrasive content	%	6.00
Solid W&D additive	%	0.60
Ratio W&D:Abrasive	%	1:10
Total solid content	%	11.30
Solids	%	17.00

Further information / application

- The car polish formulation is designed to be used as it is.
- Spray a thin layer of the formulation on the painted surface and apply using a polishing machine with a soft polishing sponge.



Your local
contact

BYK-Chemie GmbH
Abelstraße 45
46483 Wesel
Germany
Tel +49 281 670-0

info@byk.com
www.byk.com

ANTI-TERRA®, AQUACER®, AQUAMAT®, AQUATIX®, BENTOLITE®, BYK®, BYK-AQUAGEL®, BYK-DYNWET®, BYK-MAX®, BYK-SILCLEAN®, BYKANOL®, BYKCARE®, BYKETOL®, BYKJET®, BYKONITE®, BYKOPLAST®, BYKUMEN®, CARBOBYK®, CERACOL®, CERAFAK®, CERAFLOUR®, CERAMAT®, CERATIX®, CLAYTONE®, CLOISITE®, DISPERBYK®, DISPERPLAST®, FULACOLOR®, FULCAT®, GARAMITE®, GELWHITE®, HORDAMER®, LACTIMON®, LAPONITE®, NANOBYPK®, OPTIBENT®, OPTIGEL®, PURABYPK®, RECYCLOBYPK®, RHEOBYPK®, SCONA®, SILBYPK®, TIXOGEL® and VISCOBYPK® are registered trademarks of the BYK group.

The information contained herein is based on our current knowledge and experience. No warranties, guarantees and/or assurances of any kind, either express or implied, including warranties of merchantability or fitness for a particular purpose, are made regarding any products mentioned herein and data or information set forth, or that such products, data or information may be used without infringing intellectual property rights of third parties. Any information about suitability, use or application of the products is non-binding and does not constitute a commitment regarding the products' properties, use or application. Contractual terms and conditions, in particular agreed product specifications, always take precedence. We recommend that you test our products in preliminary trials to determine their suitability for your intended purpose prior to use. We reserve the right to make any changes and to update the information herein without notice.

Download
our app:
byk.com/app

