



Application Information TS-A 2

Additives for Gel Coats

Air Release Additives

Entrapped air bubbles are a common problem in manufacturing or applying unsaturated polyester gel coats. They are difficult to remove mainly because most gel coats are highly thixotropic. In addition, they are usually applied by airless spray equipment in a single pass to a wet film thickness of 400 to 500 µm. These same air bubbles ultimately develop into pinholes, which increases porosity and dramatically reduces the gel coat's water resistance.

The example (figure 1) shows a spray gel coat with and without BYK-A 555. Hot water resistance at 98 °C is dramatically improved in the samples with BYK-A 555.

The following standard additives can be used in almost all gel coat formulations to improve air release properties during manufacturing and application.

BYK-A 555 is widely used in all types of gel coats. It is the most efficient air release additive.

BYK-A 515 can also be used in various gel coats and is especially recommended for vinyl ester based systems.

BYK-A 550 is highly effective with minimal haze, and is recommended for transparent gel coats.

Impact of Air Entrapment on Hot Water Resistance

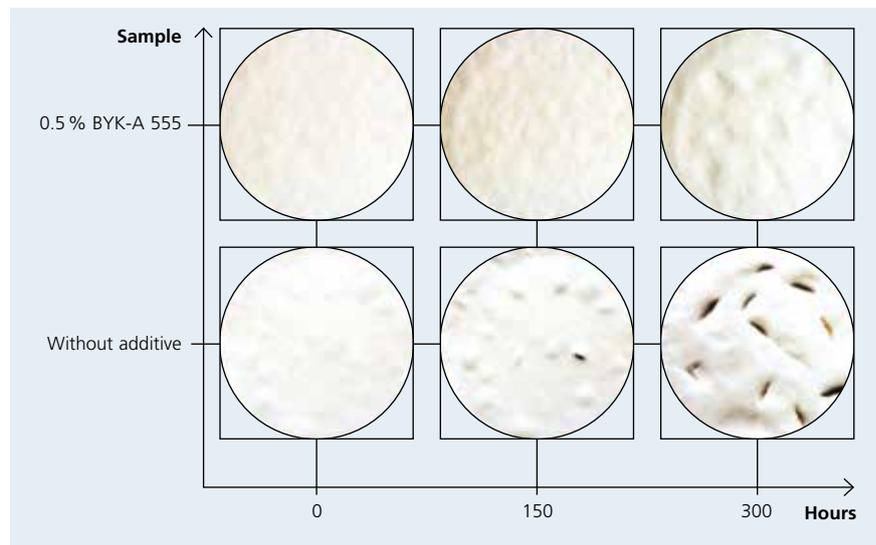


figure 1

Additives to Improve Flow/Leveling and Prevent Craters and Fisheyes

Depending on the application method, uniform flow and leveling is required for the applied gel coat. Brushed gel coats can vary in film thickness because of insufficient flow and leveling properties.

It is critical for the mold surface to be sufficiently wet by the gel coat! Poor substrate wetting occurs when the gel coat has a higher surface tension than the mold surface (figure 2).

Fisheyes develop when there are surface tension differences between the mold releasing film, the gel coat film, and dust particles (figure 3). When a dust particle falls into the gel coat film, the gel coat cannot wet the particle because of its high surface tension. The surface tension of the gel coat thus needs to be reduced in order to solve the fisheye problem.

Substrate Wetting



Poor mold surface wetting because of gel coat's high surface tension.

figure 2

Possible solutions to improve substrate wetting and eliminate fisheyes are:

Silicones in case of large surface tension differences.

Acrylate leveling additives in case of small surface tension differences.

Craters

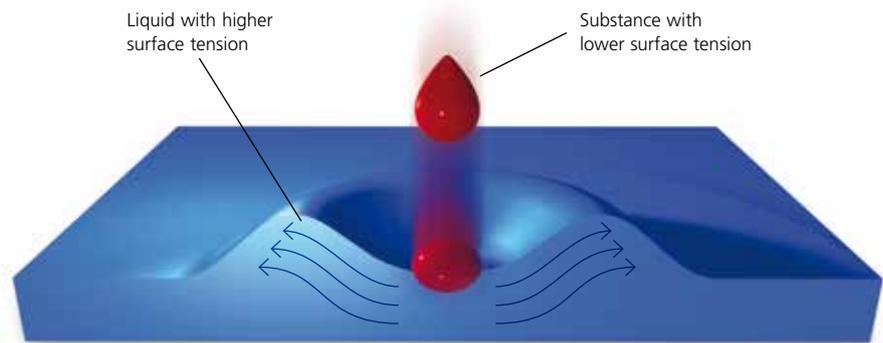


figure 3

Silicones

BYK-330 reduces the surface tension of the gel coat, improves flow and leveling, and eliminates fisheyes. Because of its controlled compatibility in the gel coat, it does not stabilize foam.

BYK-370 improves the flow and leveling of the gel coat. It is typically compatible with unsaturated polyester resins. BYK-370 is especially effective in clear gel coats.

BYK-310 is a compatible silicone that reduces surface tension and improves flow and leveling.

BYK-378 significantly reduces surface tension and provides low foam stabilization. It improves substrate wetting and prevents cratering.

Effect of BYK-330

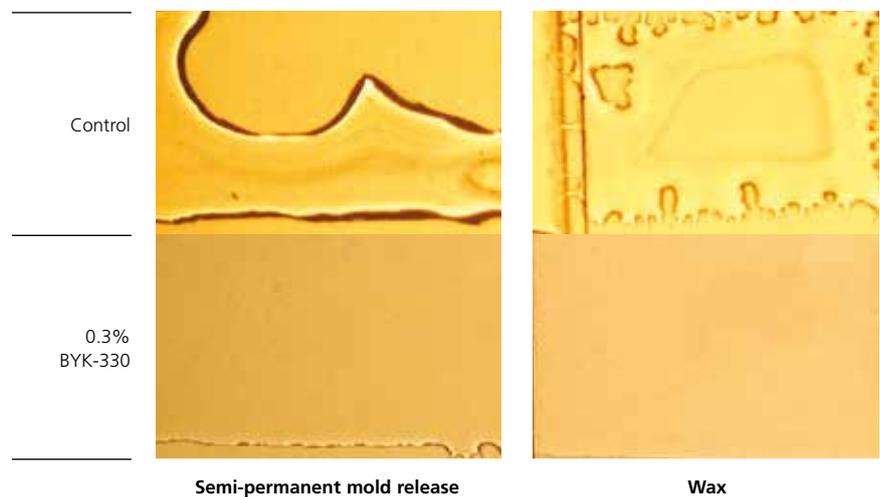



figure 4

Acrylates

BYK-S 706 is widely used in unsaturated polyester gel coats. It improves the flow and leveling properties of the applied gel coat film and helps surface deaeration. It is often used in continuous lamination processes to improve the flow and leveling of the gel coat film and prevent fisheyes. BYK-S 706 will introduce a slight turbidity in clear gel coats.

BYK-361 N improves the flow and leveling properties of the applied gel coat film and eliminates craters and fisheyes. BYK-361 N is more compatible than BYK-S 706 and can be used in clear gel coats.

Comparison of BYK-370 and BYK-330 in a Clear Gel Coat

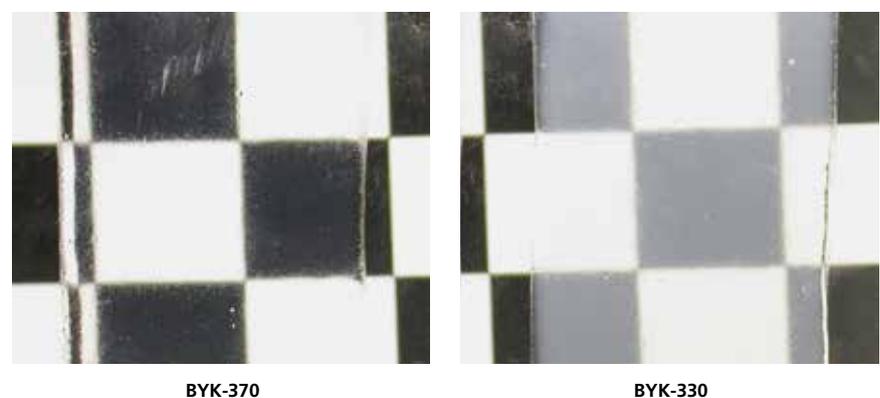

BYK-370 provides good substrate wetting without causing turbidity.

figure 5

Additive to Improve Thixotropy

Thixotropy is very important in gel coats but various problems may occur:

- no thixotropy development
- thixotropy development is too slow
- thixotropy drift over time

Since fumed silica is typically used to introduce thixotropy, it is very important that the fumed silica be well dispersed into the gel coat resin. Wetting the fumed silica can be challenging depending on the base resin type.

RHEOBYK-R 605 was developed to improve fumed silica wetting and dispersion, and enhance thixotropic properties. In order to achieve this, **RHEOBYK-R 605** should be added to the resin before the silica. This not only improves silica dispersion and enhances the thixotropic effect, but also maintains thixotropy during storage.

Vinylester Gel Coats

Hydrophilic fumed silica is usually not effective in vinylester resins. Hydrophobic fumed silica can be used to create thixotropy, but it is very difficult to obtain air release and good surface appearance. By using **RHEOBYK-R 605** in combination with hydrophilic fumed silicas, it is possible to create the required thixotropy while retaining good air release, flow, and leveling properties.

Vinylester Gel Coat with RHEOBYK-R 605

Vinylester resin	100.0 parts
BYK-A 515	0.5 parts
Fumed silica	1.8 parts
RHEOBYK-R 605	0.6 parts
Pigment	10.0 parts
Cobalt (1%)	3.0 parts
DMA (10%)	1.0 parts
Peroxide	2.0 parts

RHEOBYK-R 605 Exhibits Best Results in Vinylester Gel Coats

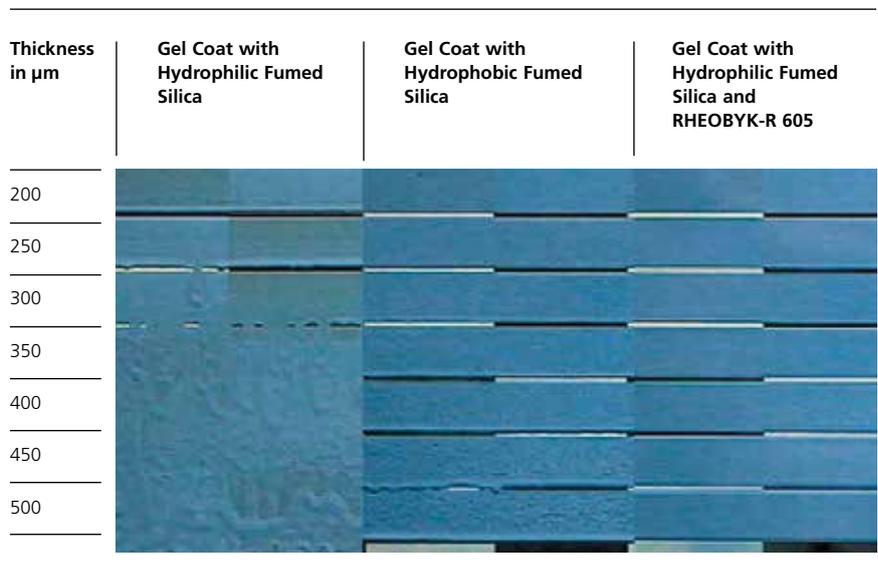


figure 6

Additives to Prevent Flooding and Floating

Pigment flooding and floating can be influenced by many variables. The most important variables are: the type of pigments or pigment mixtures, the grinding resin, degree of dispersion and pigment stabilization, the thixotropy of the gel coat, and the application method. It is critical that the pigments used are properly dispersed in the polyester resin, and properly stabilized after grinding so that re-agglomeration and uncontrolled flocculation do not occur.

There are basically two possible approaches for addressing flooding and floating problems:

1. Stabilizing the Pigmented System via Controlled Flocculation of the Pigments

In this case, the wetting and dispersing additive is able to develop a loose bridging network between the pigment particles (figure 7). Typical products are **BYK-W 940**, **BYK-W 980** and **BYK-220S**.

The advantage of these products is that they do not dramatically influence the thixotropy of the gel coat. They should be added to the system before the pigment grinding stage. In some cases, it is possible to correct flooding and floating by post-adding **BYK-W 940** or **BYK-220S** to the final gel coat.

2. Stabilizing the Pigmented System via Deflocculation of Pigments

Using high molecular weight block copolymers with many pigment affinic groups provides excellent steric stabilization, thereby preventing pigment flocculation. This stabilizes the color strength and hue of pigments in gel coats and pigment concentrates.

Typical products are **DISPERBYK-2163**, **DISPERBYK-171** and **DISPERBYK-192**. These additives must be introduced in the pigment grinding stage. They are highly effective, and mainly used in color pastes for gel coats.

It is important to check for possible detrimental effects on the thixotropy of the final gel coat. The additive's wetting effect on fumed silica may reduce the fumed silica's ability to develop thixotropy.

Controlled Flocculation

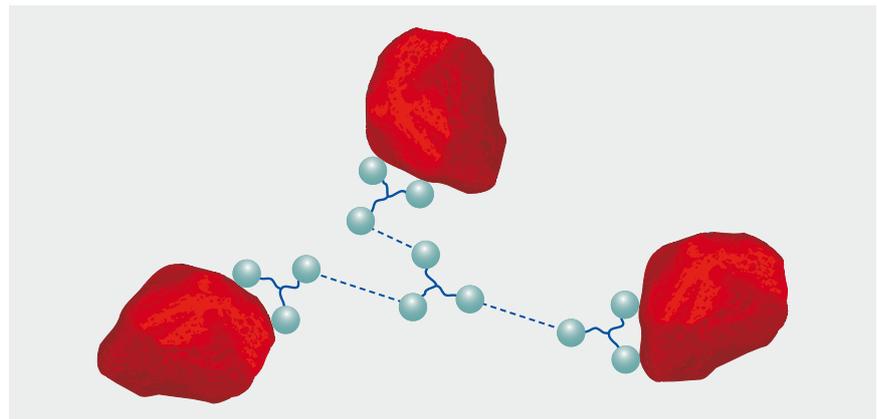


figure 7

Deflocculation with High Molecular Weight Block Copolymers

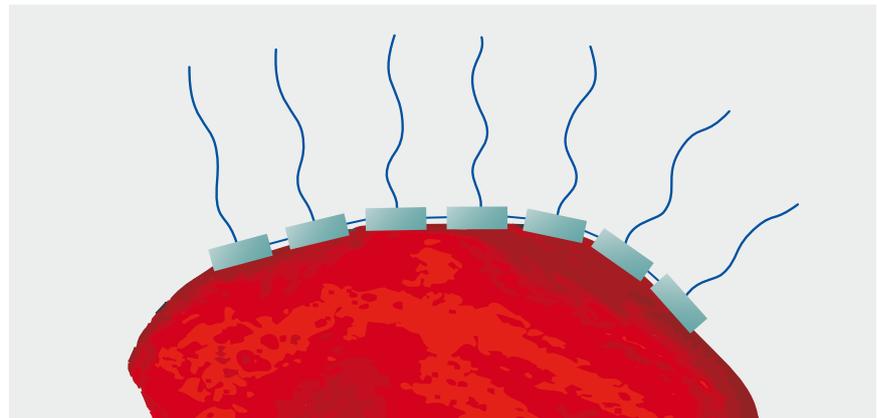


figure 8

Additives to Prevent Porosity


Porosity is a well-known phenomenon and one of the hardest to evaluate. The effect is strongly dependent on the surface tension of the mold caused by the mold release agent, the surface tension of the gel coat, and the efficiency of the air release additive. The type of peroxide used should also be taken into consideration.

The gel coat's surface tension has to be adjusted to the surface tension of the release agent, whereas wax-based release agents are easier to wet than others. We recommend surface-active additives such as **BYK-A 525** for smaller adjustments and **BYK-330** for larger adjustments.


An air release additive can support the displacement of air on the mold's surface. **BYK-A 515** or **BYK-A 555** can be used to accomplish this.

Best results have been achieved by combining a surface-active additive with an air release additive (figure 9).

Porosity

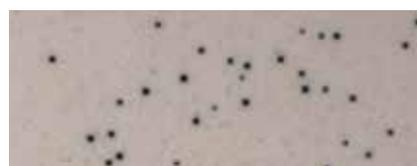

Without additive

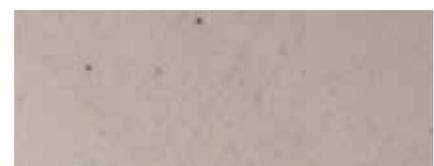

With 0.25 % BYK-A 515 + 0.25 % BYK-A 525

figure 9

Anti-tack Additives

Sometimes it is necessary to step on a gel coat because of the mold size (boat hulls) or to fix surface defects. If the surface of the gel coat is sticky, the worker would destroy the coating by stepping on it. BYK's range of anti-tack additives helps overcome this issue by covering the surface of the gel coat with a non-sticky film (figure 10).

A lab test can easily be performed with a cotton pad. One hour after application, the pad is placed on the gel coat's surface and a 1 kg weight

is positioned on the pad. After one minute, the weight is removed and the pad is lifted from the gel coat by picking it up at the center (figure 11).

Interlaminar adhesion is normally not affected by the anti-tack additives, but should be carefully checked in each system (figure 12).


BYK-S 780, a wax dispersion, is recommended for all systems, especially for vinylester resins where interlaminar adhesion is not required.

BYK-S 781, a combination of waxes with polar components, is a good choice for all systems where interlaminar adhesion is required.

BYK-S 782, a combination of modified waxes, is designed for applications at higher temperatures (i.e. in the summer). It can be applied in every system that requires interlaminar adhesion. The additive can be melted before use so that it is easier to handle.

Step-on Test

Gel coat with BYK-S 780

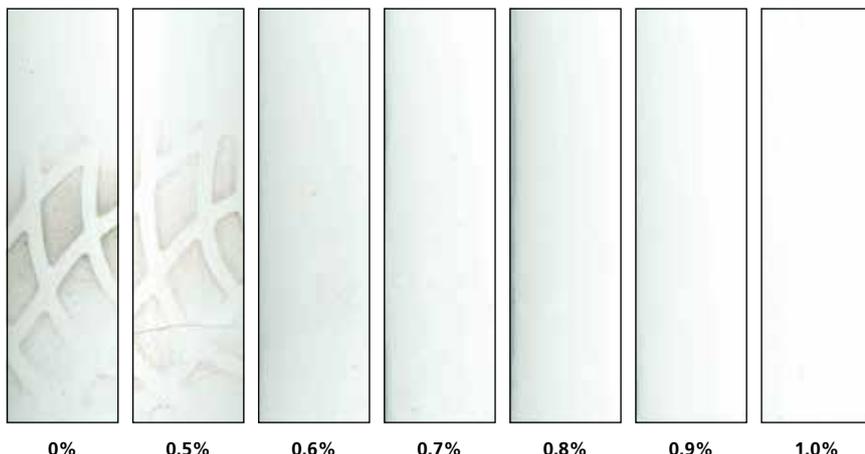

Dosage of BYK-S 780 based upon gel coat

figure 10

Cotton Pad Test



Without additive



With BYK-S 780

figure 11

Test of Interlaminar Adhesion

Perfect adhesion even with 1% BYK-S 781 on gel coat



Laminate after

1 day

4 days

figure 12

Additives for Gel Coats – Summary

	Pigmented		Transparent Gel Coats
	Spray Gel Coats	Brush Gel Coats	
Air Release			
BYK-A 500			Good
BYK-A 501	Good	Good	
BYK-A 515	Excellent	Excellent	
BYK-A 550			Excellent
BYK-A 555	Excellent	Excellent	
Flooding and Floating			
BYK-220S	Excellent	Excellent	
BYK-W 940	Excellent	Excellent	
BYK-W 980	Good	Good	
DISPERBYK-166	Good	Good	
DISPERBYK-167	Excellent	Excellent	
DISPERBYK-171	Good	Good	
DISPERBYK-192	Excellent	Excellent	
Thixotropy			
RHEOBYK-R 605	Excellent	Excellent	Good
Flow and Leveling			
BYK-306	Good	Good	
BYK-330	Excellent	Excellent	
BYK-370	Good	Good	Excellent
BYK-378	Excellent	Excellent	
BYK-S 706	Excellent	Good	
BYK-361	Good	Good	Excellent
Porosity			
BYK-330	Good		
BYK-A 515	Excellent		
BYK-A 525	Excellent		
BYK-A 530	Good		
Anti-tack			
BYK-S 780	Good	Good	
BYK-S 781	Excellent	Good	
BYK-S 782	Excellent	Excellent	

■ Excellent

■ Good

figure 13

For more information about our additives and instruments, as well as our additive sample orders please visit:

www.byk.com

Additives:

BYK-Chemie GmbH
P.O. Box 100245
46462 Wesel
Germany
Tel +49 281 670-0
Fax +49 281 65735

info@byk.com

Instruments:

BYK-Gardner GmbH
P.O. Box 970
82534 Geretsried
Germany
Tel +49 8171 3493-0
+49 800 427-3637
Fax +49 8171 3493-140

info.byk.gardner@altana.com



Additive Guide



ACTAL®, ADD-MAX®, ADD-VANCE®, ADJUST®, ADVITROL®, ANTI-TERRA®, AQUACER®, AQUAMAT®, AQUATIX®, BENTOLITE®, BYK®, BYK-DYNWET®, BYK-SILCLEAN®, BYKANOL®, BYKETOL®, BYKJET®, BYKO2BLOCK®, BYKOPLAST®, BYKUMEN®, CARBOBYK®, CERACOL®, CERAFAK®, CERAFLOUR®, CERAMAT®, CERATIX®, CLAYTONE®, CLOISITE®, DISPERBYK®, DISPERPLAST®, FULACOLOR®, FULCAT®, GARAMITE®, GELWHITE®, HORDAMER®, LACTIMON®, LAPONITE®, MINERAL COLLOID®, MINERPOL®, NANOBYK®, OPTIBENT®, OPTIFLO®, OPTIGEL®, PAPERBYK®, PERMONT®, POLYAD®, PRIEX®, PURE THIX®, RECYCLOBLEND®, RECYCLOSORB®, RECYCLOSTAB®, RHEOBYK®, RHEOCIN®, RHEOTIX®, SCONA®, SILBYK®, TIXOGEL®, VISCOBYK® and Y 25® are registered trademarks of the BYK group.

The information herein is based on our present knowledge and experience. The information merely describes the properties of our products but no guarantee of properties in the legal sense shall be implied. We recommend testing our products as to their suitability for your envisaged purpose prior to use. No warranties of any kind, either express or implied, including warranties of merchantability or fitness for a particular purpose, are made regarding any products mentioned herein and data or information set forth, or that such products, data or information may be used without infringing intellectual property rights of third parties. We reserve the right to make any changes according to technological progress or further developments.

This issue replaces all previous versions – Printed in Germany