

APPLICATION INFORMATION
**PTFE-FREE TEXTURES IN POWDER COATINGS
WITH CLAYTONE AND GARAMITE**



Content

- 03 Introduction
- 04 CLAYTONE and GARAMITE in powder coatings
- 05 Evaluation of optical appearance, structure, and texture effects
- 06 Hybrid powder coating systems (polyester + epoxy)
- 09 HAA powder coating systems (polyester + β -hydroxyalkyl amide)

Introduction

Polytetrafluoroethylene (PTFE) is a typical representative of perfluoroalkyl and polyfluoroalkyl substances (PFAS) that provides unique properties for powder coatings. The effects range from scratch resistance to the creation of fine textures. In particular, the robust, fine texture is a desired design in the market today. It covers functional as well as decorative demands. Its usage has been increasingly critically assessed at a global level for some time now, because products from this group of chemicals are suspected of being harmful to health. BYK provides a solution that avoids the use of PFASs entirely and still obtains a fine texture design in powder coatings by using CLAYTONE and GARAMITE. It helps to fulfill the demand for matt, fine texture designs without fear of rapid emergency changes in the formulation due to regulatory restrictions.

For additional information on additives and technical topics, please contact us:
powderlab.BYK.Wesel@altana.com

Note

To ensure the best appearance and full functionality, please open in Adobe Acrobat.

CLAYTONE and GARAMITE in powder coatings

Various products of the product lines CLAYTONE and GARAMITE can be used to create structure or texture finishes by increasing the melt viscosity and providing predictable rheology for powder coatings. The resulting fine texture finishes offer an alternative to PTFE-based additives. CLAYTONE and GARAMITE types offer a selection of visual effects. Differences in the combination of gloss level, texture fineness and dosage reliability can be achieved and selected by using these types. These effects are supported by the composition of the formulation.

CLAYTONE shows a distinct strength in hybrid systems (polyester + epoxy), while GARAMITE shows its strength in HAA systems (polyester + β -hydroxyalkyl amide). Nevertheless, both product lines are suitable for all types of powder coating resin systems.

The additives need to be mixed with resin, hardener, pigments, and other raw materials in a high-speed mixer and extruded afterwards. Good dispersion of the additive by the extruder promotes texture development.

Production process of powder coatings



Net weight



Pre-mixing



Extrusion




Grinding



Sieving



Application

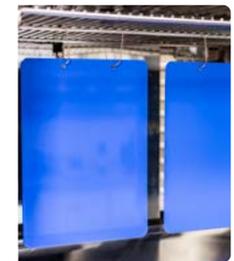

Curing

Evaluation of optical appearance, structure, and texture effects

The texture effect achieved can be evaluated visually or, for example, with a 3D surface scan using spectro2profiler provided by BYK Gardner. This instrument takes multiple pictures and generates a 3D topography of the coating surface.

The explanation of 3D topography is slightly more complex and is indicated by a color scale:

- An even and homogenous color indicates a smooth surface.
- A color gradient from yellow to green shows differences between the minimum and maximum height, which can be perceived as structure.
- A color gradient from yellow to violet shows even higher differences between the minimum and maximum height, which can be seen as texture.



Color scale



Minimum
No texture

Maximum
Texture

The measurement area for the 3D topography is approx. 15 mm x 15 mm, while the size of the photographed samples is approx. 60 mm x 60 mm.

Hybrid powder coating systems (polyester + epoxy)

Hybrid formulations include a leveling additive for smooth finishes. To achieve a texture effect, PTFE wax-based additives are used. With the CLAYTONE and GARAMITE product lines, the texture effect is created without PTFE.

These different starting point formulations show various possibilities with BYK additives. CLAYTONE and GARAMITE can be used with or without a leveling additive to achieve different texture appearances.

Starting point formulations

Raw material	Control (no texture)	Standard texture formulation	Without leveling additive		With leveling additive	
			2.0% Rheology additive	4.0% Rheology additive	2.0% Rheology additive	4.0% Rheology additive
Polyester resin (AV ~ 35 mg KOH/g)	46.6	46.6	46.6	46.6	46.6	46.6
Epoxy resin (EEW ~ 770 g/eq)	19.4	19.4	19.4	19.4	19.4	19.4
Titanium dioxide	5.2	5.2	5.2	5.2	5.2	5.2
Barium sulfate	25.4	25.4	25.4	25.4	25.4	25.4
Organic blue pigment	2.0	2.0	2.0	2.0	2.0	2.0
Benzoin	0.4	0.4	0.4	0.4	0.4	0.4
Leveling additive	1.0	0.8	-	-	0.8	0.8
PTFE wax additive	-	0.5	-	-	-	-
CLAYTONE or GARAMITE type	-	-	2.0	4.0	2.0	4.0
Total	100.0	100.3	101.0	103.0	101.8	103.8

T.01

Processing instructions

Extruder	Twin screw
	Heating zone 90 °C–105 °C
	Shaft speed 350 rpm

Application


Powder gun	Voltage	70 kV
	Thickness minimum	70 µm

Typically used additives are GARAMITE-1210, GARAMITE-7305, CLAYTONE-APA, and CLAYTONE-HY, which create various gloss and texture effects. CLAYTONE-HY can be used to achieve

similar texture effects compared to PTFE standard formulations. If CLAYTONE-HY is combined with a leveling additive, the gloss might be increased compared to the samples without.

CLAYTONE-HY compared to PTFE wax additive in hybrid system

Optical appearance

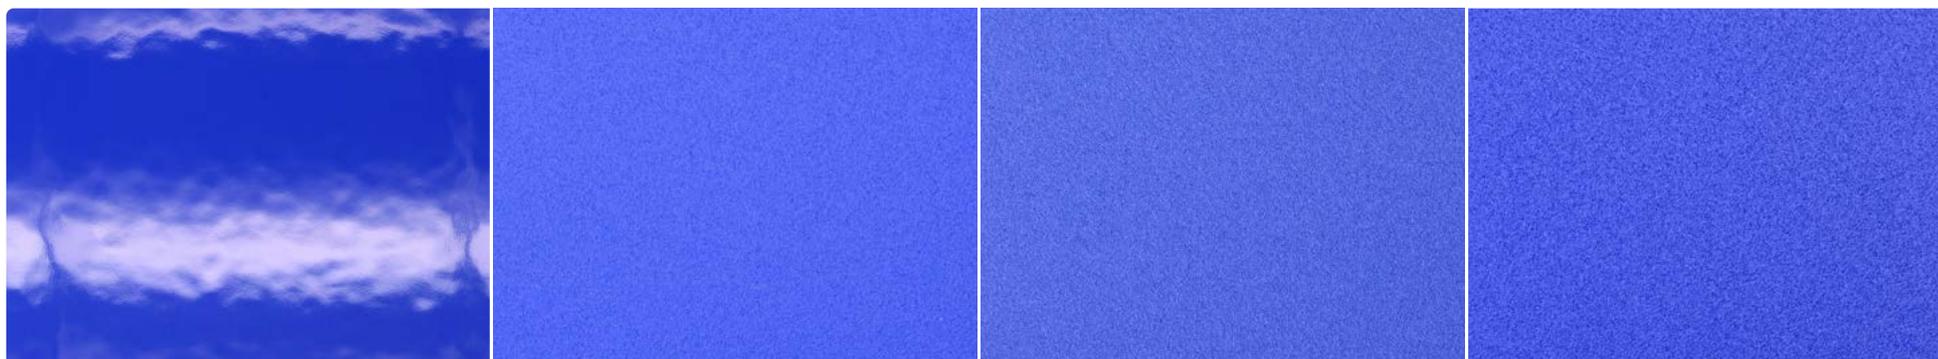


Control (no texture)

Standard texture formulation

4.0 % CLAYTONE-HY without leveling additive

4.0 % CLAYTONE-HY with leveling additive

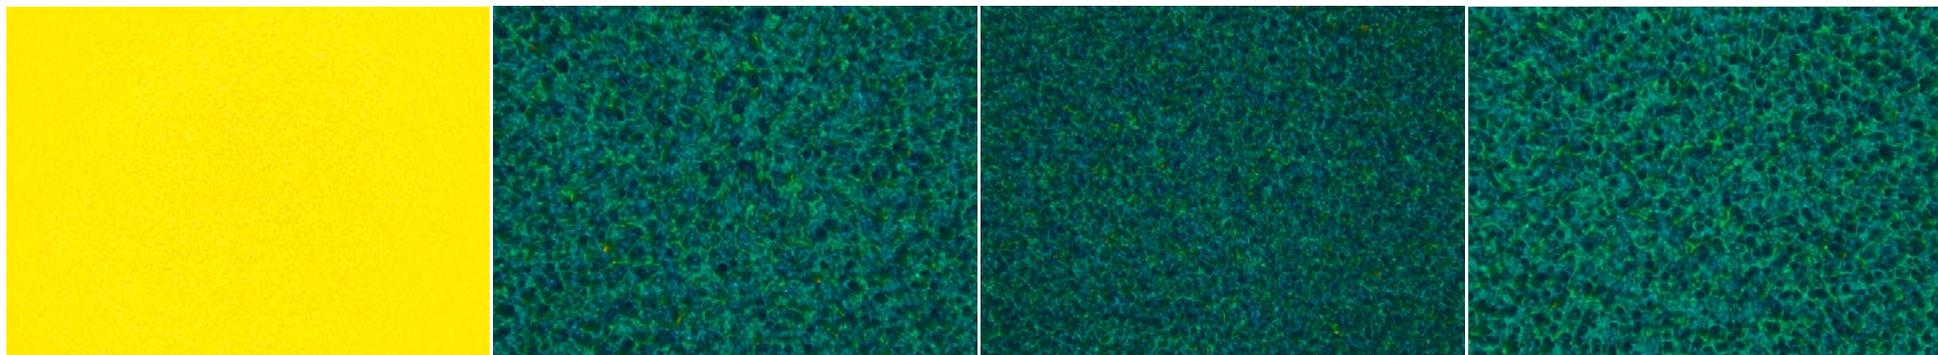


3D topography

The usage of the other recommended additives leads to different structures and texture effects, which provides a wide variety simply by using different dosages of the additives. The samples differ in gloss values as well as in structure appearance, which can be seen in the 3D

typography of the surfaces. GARAMITE-7305 provides smoother surfaces, while GARAMITE-1210 creates a stronger texture. Different dosages of CLAYTONE-APA provide matt surfaces, which become more matt with higher dosages.


Comparison of GARAMITE-1210 and GARAMITE-7305 in hybrid system

Optical appearance

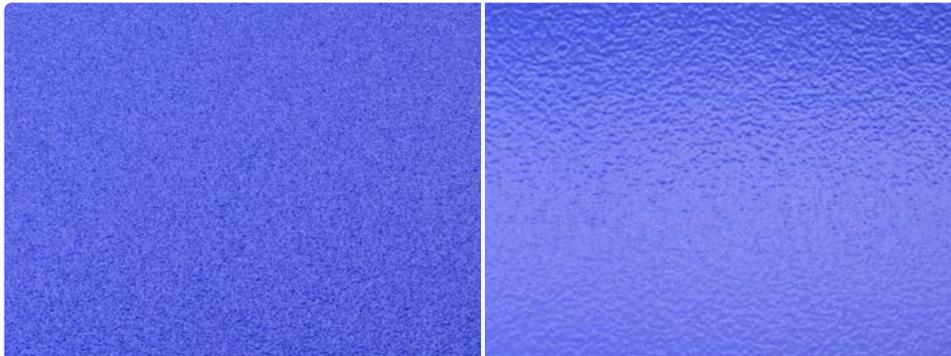

4.0 % GARAMITE-1210


4.0 % GARAMITE-7305

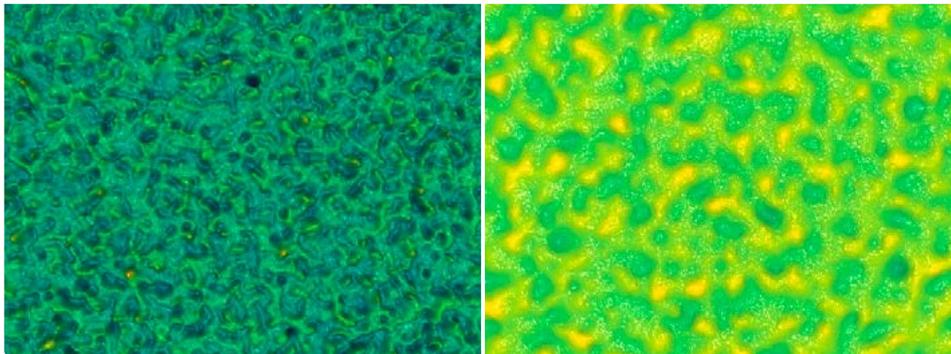

3D topography


Different dosages of CLAYTONE-APA in hybrid system

Optical appearance

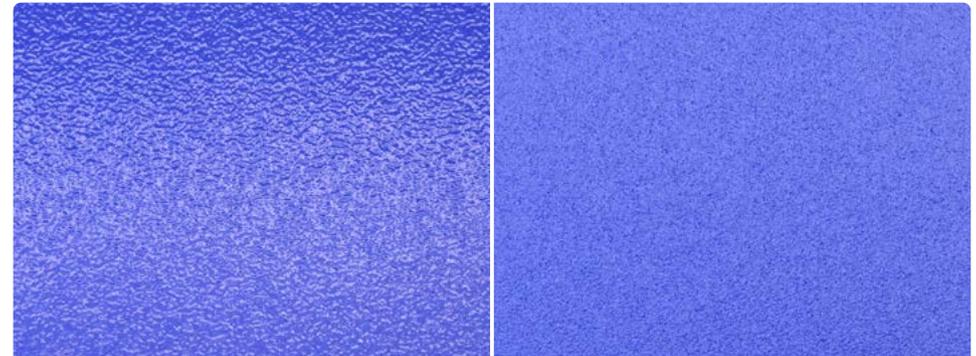

2.0 % CLAYTONE-APA

4.0 % CLAYTONE-APA

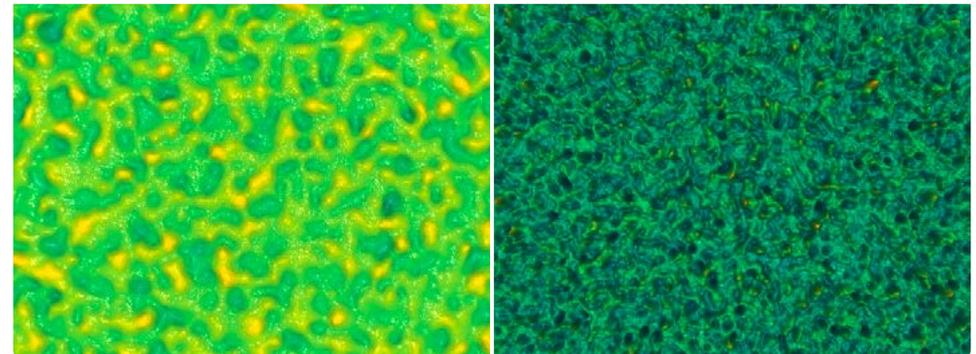

3D topography

HAA powder coating systems (polyester + β -hydroxyalkyl amide)

HAA powder coating systems include a leveling additive for smooth finishes. To achieve a texture effect, PTFE wax-based additives are used. With the CLAYTONE and GARAMITE product lines, the texture effect is created without PTFE.

These different starting point formulations show various possibilities with BYK additives. CLAYTONE and GARAMITE can be used with or without a leveling additive to achieve different texture appearances.

Starting point formulations

Raw material	Control (no texture)	Standard texture formulation	With leveling additive		
			2.0% Rheology additive	4.0% Rheology additive	
Polyester resin (AV ~ 33 mg KOH/g)		70.4	70.4	70.4	70.4
HAA (Ratio 95:5)		3.7	3.7	3.7	3.7
Titanium dioxide		15.0	15.0	15.0	15.0
Barium sulfate		9.1	9.1	9.1	9.1
Carbon black		0.4	0.4	0.4	0.4
Benzoin		0.4	0.4	0.4	0.4
Leveling additive		1.0	0.8	0.8	0.8
PTFE wax additive		-	0.5	-	-
CLAYTONE or GARAMITE type		-	-	2.0	4.0
Total		100.0	100.3	101.8	103.8

T.02

Processing instructions

Extruder Twin screw
 Heating zone 90 °C–100 °C
 Shaft speed 350 rpm

Application

Powder gun Voltage 70 kV
 Thickness minimum 70 μ m


Typically used additives are GARAMITE-1210 and CLAYTONE-HY, which create various gloss and texture effects. GARAMITE-1210 can be used to achieve almost the same effect compared to a PTFE standard solution.

GARAMITE-1210 compared to PTFE wax additive in HAA system


Optical appearance





Control (no texture)



Standard texture formulation



4.0 % GARAMITE-1210

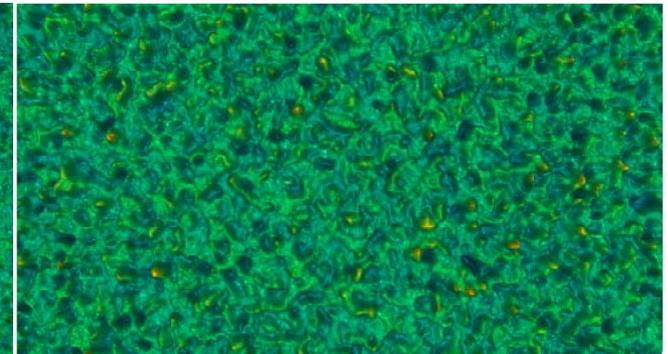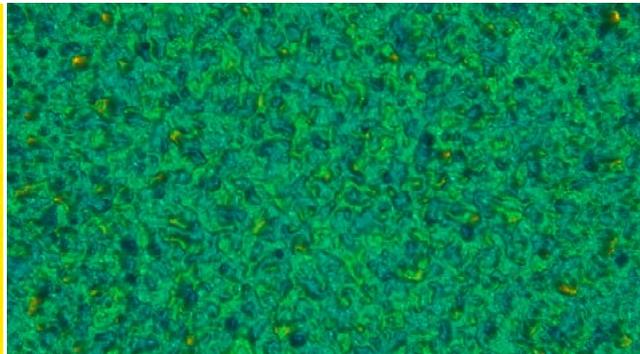

3D topography

BYK-Chemie GmbH
 Abelstraße 45
 46483 Wesel
 Germany
 Tel +49 281 670-0
 Fax +49 281 65735

info@byk.com
www.byk.com

ADD-MAX®, ADD-VANCE®, ANTI-TERRA®, AQUACER®, AQUAMAT®, AQUATIX®, BENTOLITE®, BYK®, BYK-AQUAGEL®, BYK-DYNWET®, BYK-MAX®, BYK-SILCLEAN®, BYKANOL®, BYKCARE®, BYKETOL®, BYKJET®, BYKO2BLOCK®, BYKONITE®, BYKOPLAST®, BYKUMEN®, CARBOBYK®, CERACOL®, CERAFAK®, CERAFLOUR®, CERAMAT®, CERATIX®, CLAYTONE®, CLOISITE®, DISPERBYK®, DISPERPLAST®, FULACOLOR®, FULCAT®, GARAMITE®, GELWHITE®, HORDAMER®, LACTIMON®, LAPONITE®, MINERPOL®, NANOBYK®, OPTIBENT®, OPTIFLO®, OPTIGEL®, POLYAD®, PRIEX®, PURABYK®, PURE THIX®, RECYCLOBLEND®, RECYCLOBYK®, RECYCLOSSORB®, RECYCLOSTAB®, RHEOBYK®, RHEOCIN®, RHEOTIX®, SCONA®, SILBYK®, TIXOGEL® and VISCOBYK® are registered trademarks of the BYK group.

The information herein is based on our present knowledge and experience. The information merely describes the properties of our products but no guarantee of properties in the legal sense shall be implied. We recommend testing our products as to their suitability for your envisaged purpose prior to use. No warranties of any kind, either express or implied, including warranties of merchantability or fitness for a particular purpose, are made regarding any products mentioned herein and data or information set forth, or that such products, data or information may be used without infringing intellectual property rights of third parties. We reserve the right to make any changes according to technological progress or further developments.

This issue replaces all previous versions.

